



## Tracking Electronic Pathways in Energy Materials by Low Voltage Scanning Electron Microscopy

Bentzen, Janet Jonna; Thydén, Karl Tor Sune

*Publication date:*  
2016

*Document Version*  
Publisher's PDF, also known as Version of record

[Link back to DTU Orbit](#)

*Citation (APA):*

Bentzen, J. J., & Thydén, K. T. S. (2016). *Tracking Electronic Pathways in Energy Materials by Low Voltage Scanning Electron Microscopy*. Poster session presented at SCANDEM 2016, Trondheim, Norway.

---

### General rights

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal

If you believe that this document breaches copyright please contact us providing details, and we will remove access to the work immediately and investigate your claim.



# Tracking Electronic Pathways in Energy Materials by Low Voltage Scanning Electron Microscopy


Janet J. Bentzen and Karl T. S. Thydén

Department of Energy Conversion and Storage, Technical University of Denmark – Risø Campus


## Introduction

Electrodes for energy conversion devices such as solid oxide fuel cells (SOFC) and electrolysis cells (SOEC) commonly consist of mixtures of electronically and ionically conducting ceramic and metallic materials in order to transport electrons and facilitate charge transfer to/from the electrolyte. For optimal performance it is paramount that the electronically conducting phases are well interconnected throughout the electrodes to create the required electronic connection from the electrolyte to the external circuit. Applying low voltage scanning electron microscopy and surface potential contrast [1] the interconnected electronic pathways within the electrodes can be tracked and evaluated. We here present examples of visualization of electronically percolating phases in electrodes for SOFC, SOEC, and devices for electrochemical reduction of NO<sub>x</sub> from exhaust gas from vehicles.

## Results and discussion

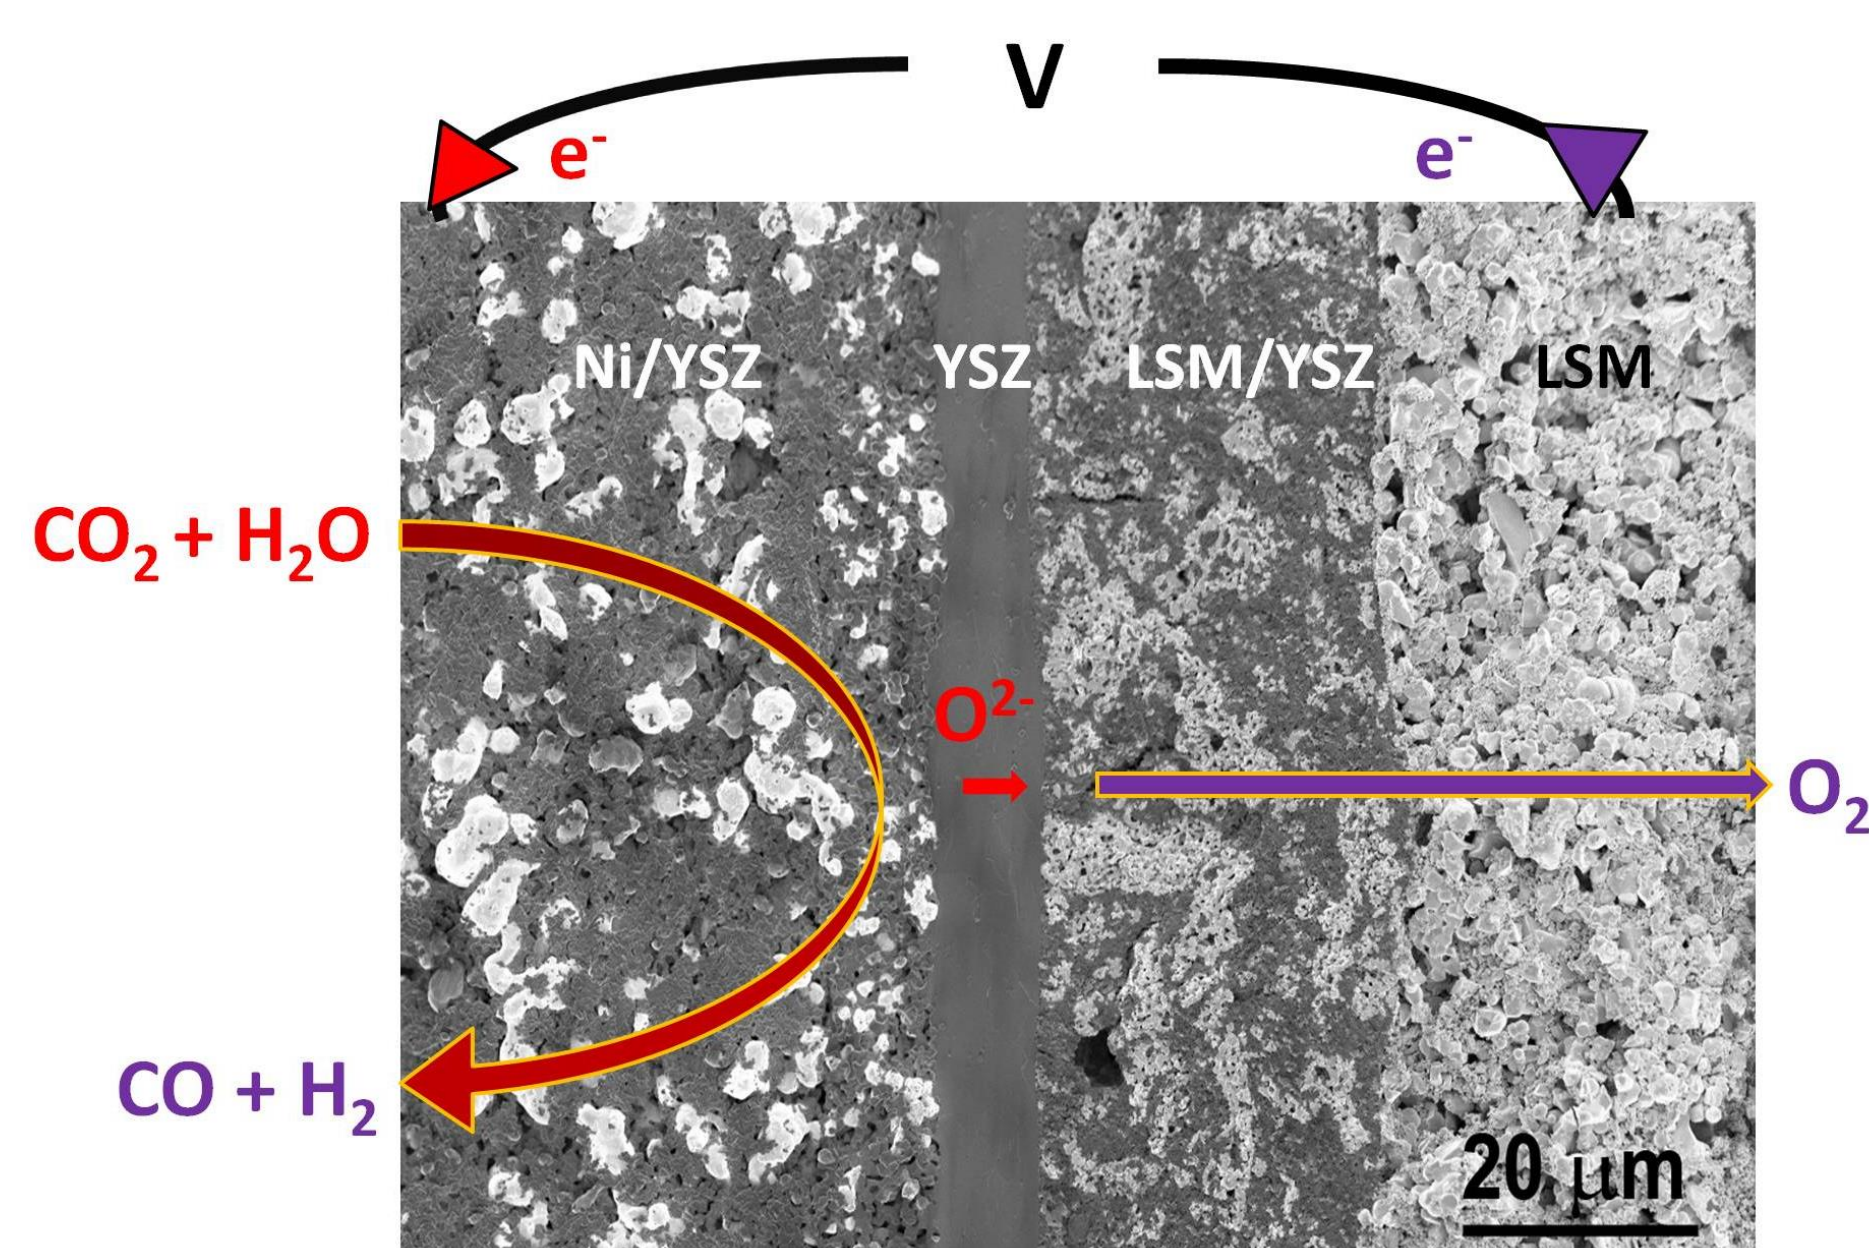


Principle of a solid oxide electrolyzer cell (SOEC), and illustration of the tracking of the electronic pathways in both electrodes.

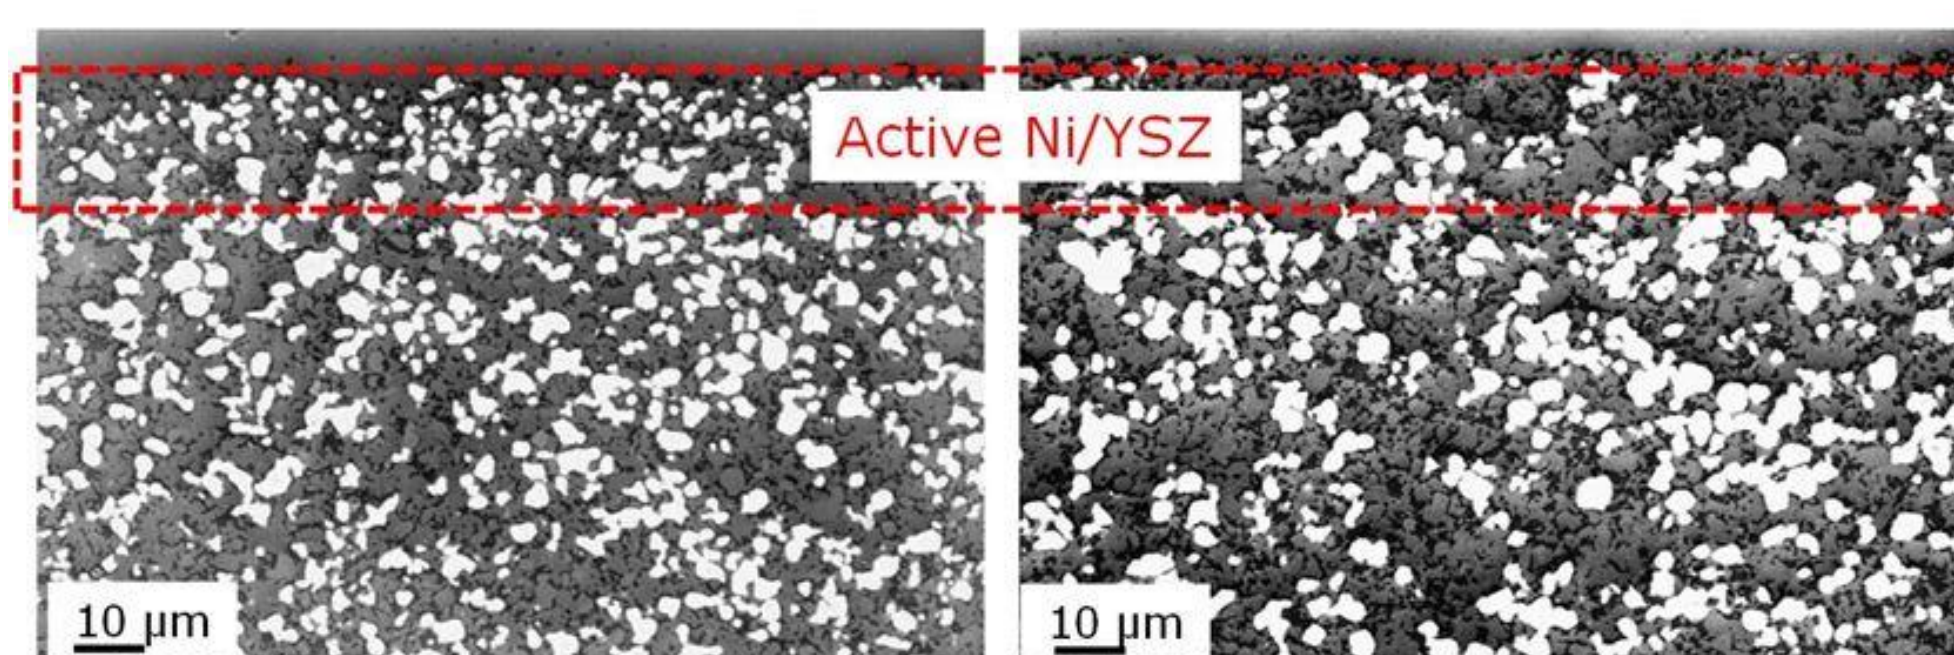


Visualization of the degradation of the contact between the Ni/YSZ electrode and the YSZ electrolyte in a solid oxide electrolyzer cell. Left image: Reference. Right image: After more than 4000 h of electrolysis.

## Experimental


The microstructural investigations were performed using FEGSEMs Zeiss Supra 35 and Zeiss Merlin applying acceleration voltages in the range 0.9 kV to 1.3 kV. Many materials have a secondary emission coefficient  $\sigma$  higher than 1 in the low voltage range [2]. This is illustrated in the case of Ni in the schematic drawing below. The in-lens secondary detector in a Zeiss Supra 35 microscope mainly picks up the part of the secondary signal that is produced directly by the primary electrons (the SE1 signal); e.g. an in-lens image of an SOFC Ni electrode at 1 kV will therefore show the percolating Ni with an emission coefficient around 1.3 provided that the sample is electrically connected to the stage. Contrary to this, the non-percolating Ni and the YSZ will charge until the barrier for secondary emission is so high that the sum of the backscatter coefficient and  $\sigma$  is 1. They will in other words be imaged with a secondary emission coefficient around 0.7.

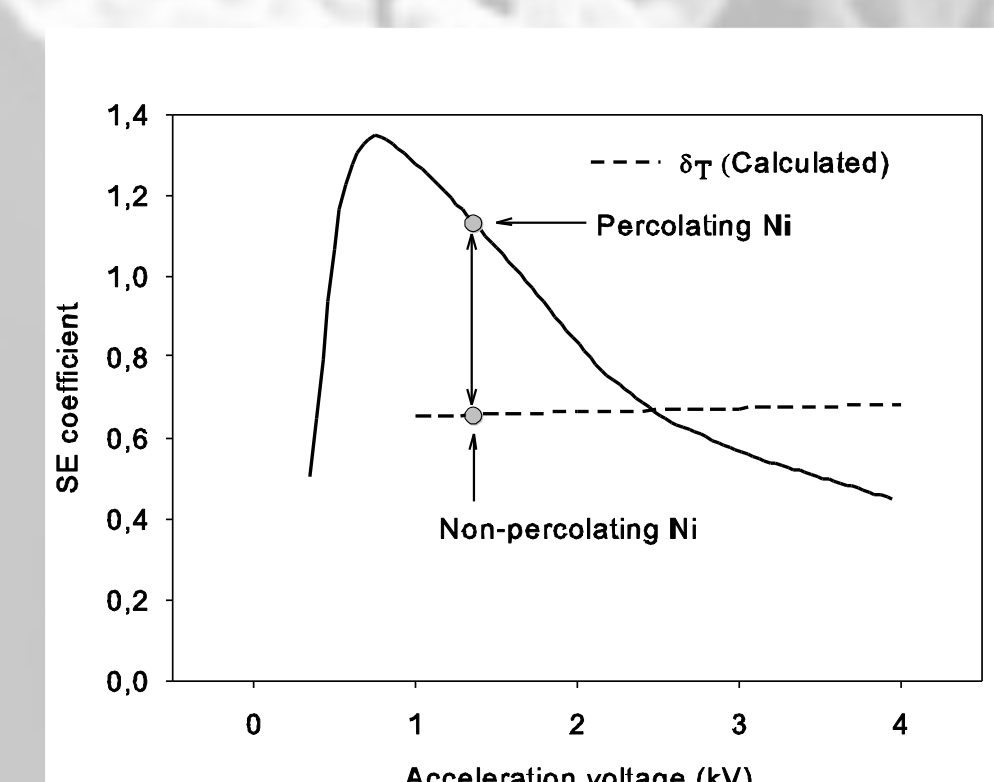


Secondary electron coefficient for Ni as a function of acceleration voltage.

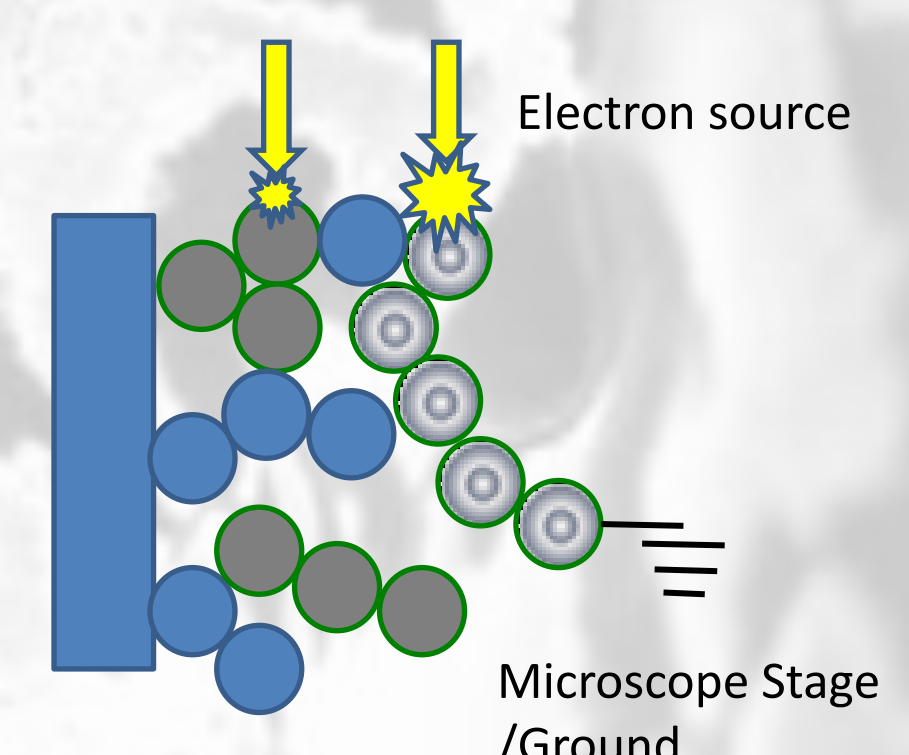

A schematic drawing illustrating the percolation contrast mechanism.

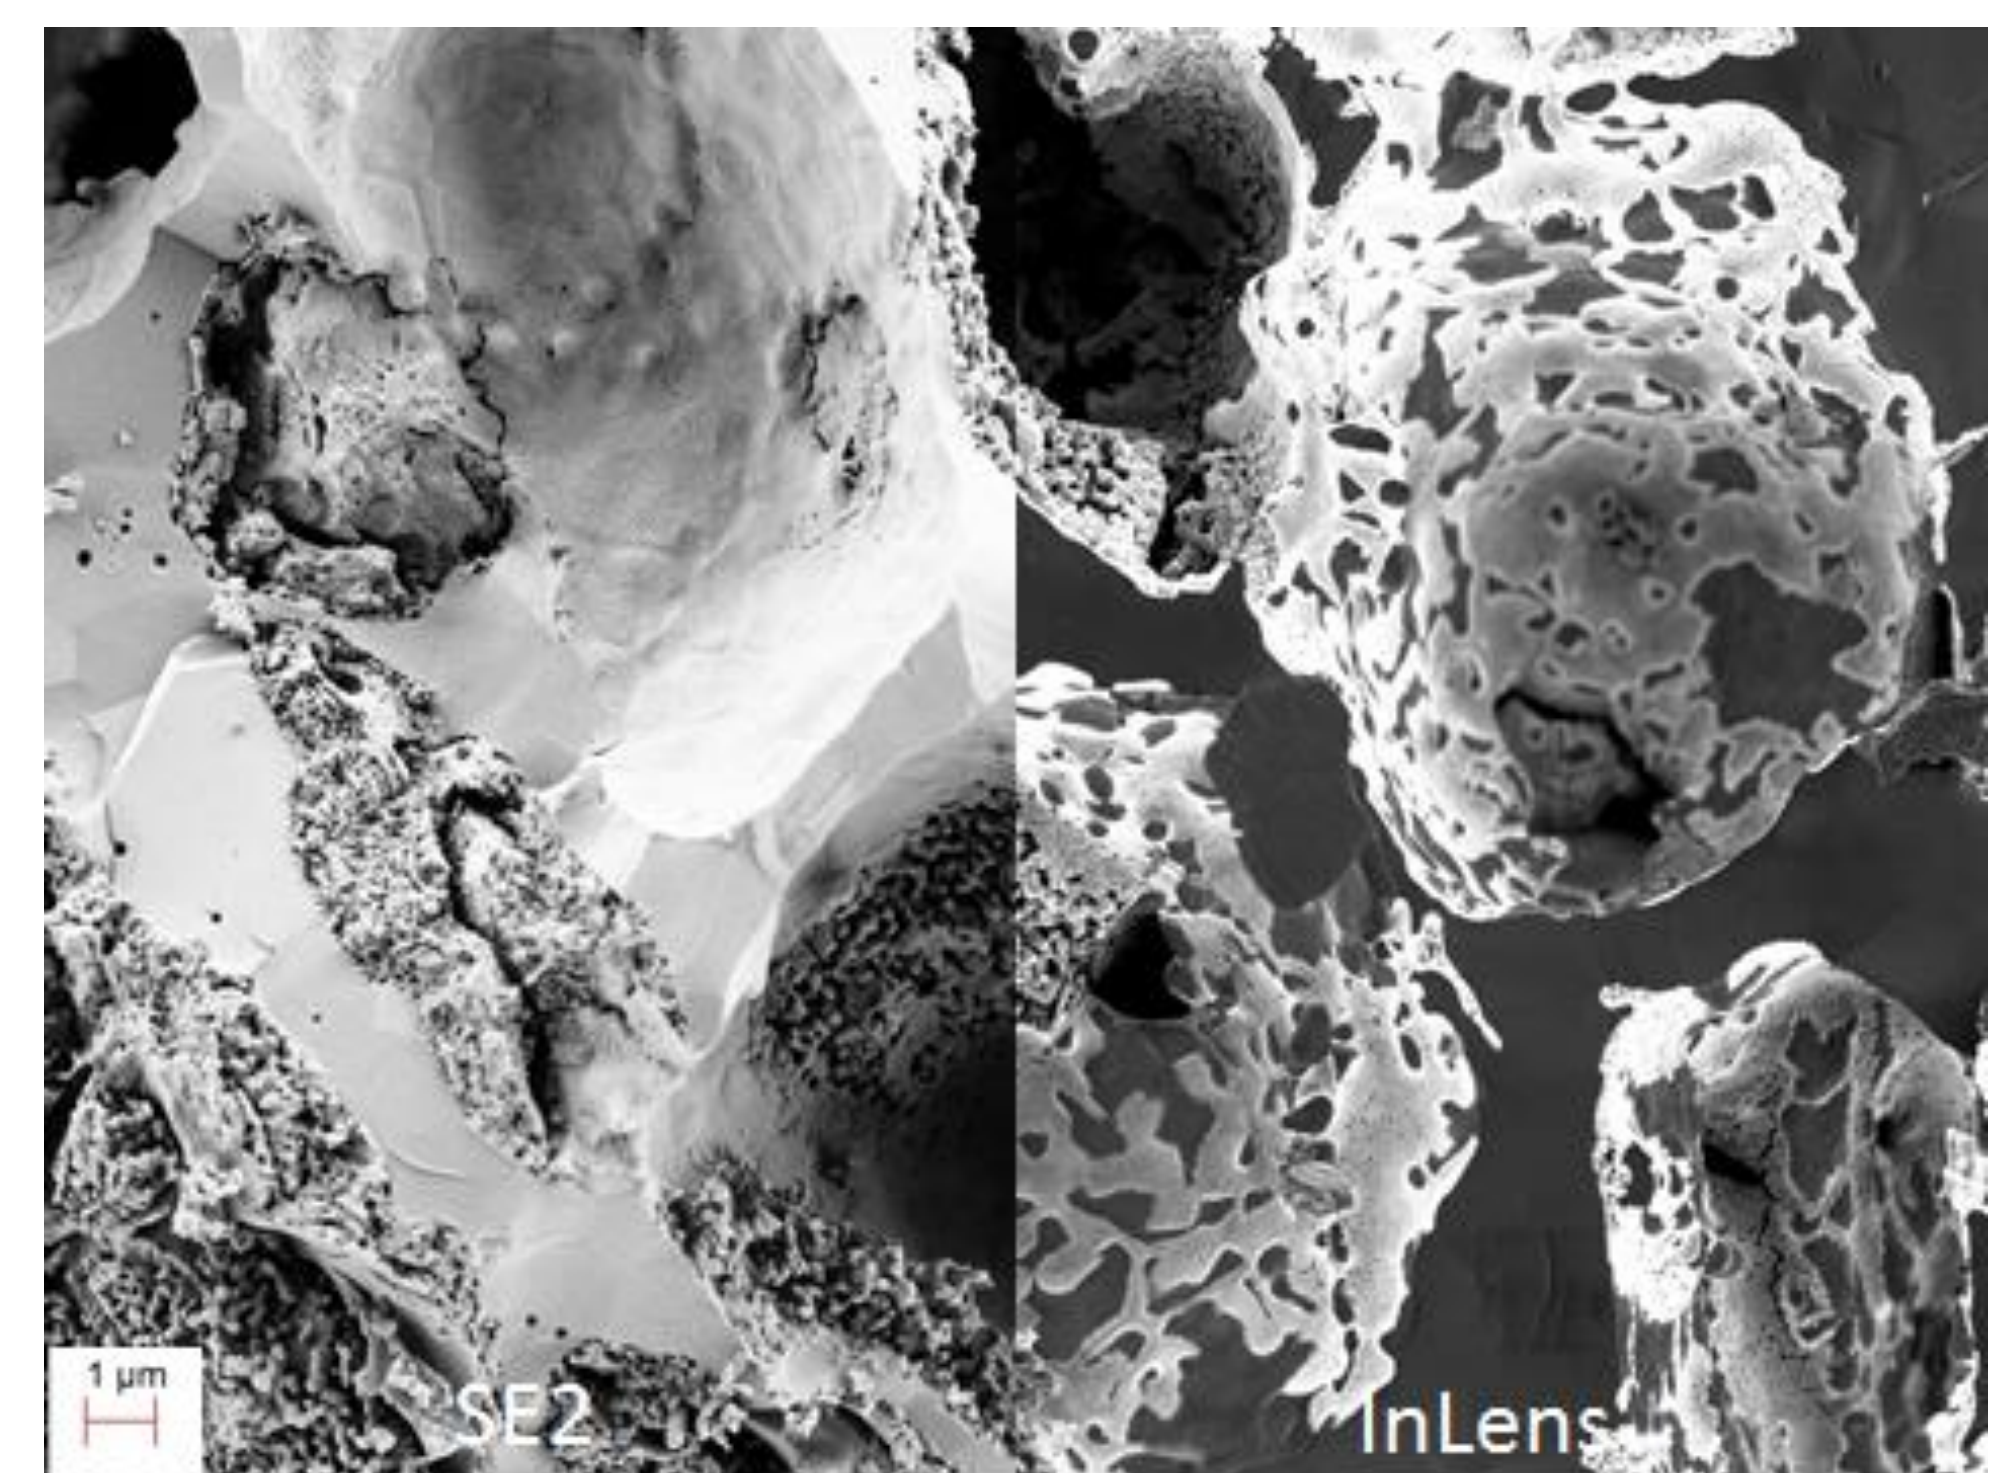

SE2 and InLens images revealing the electronic pathways.

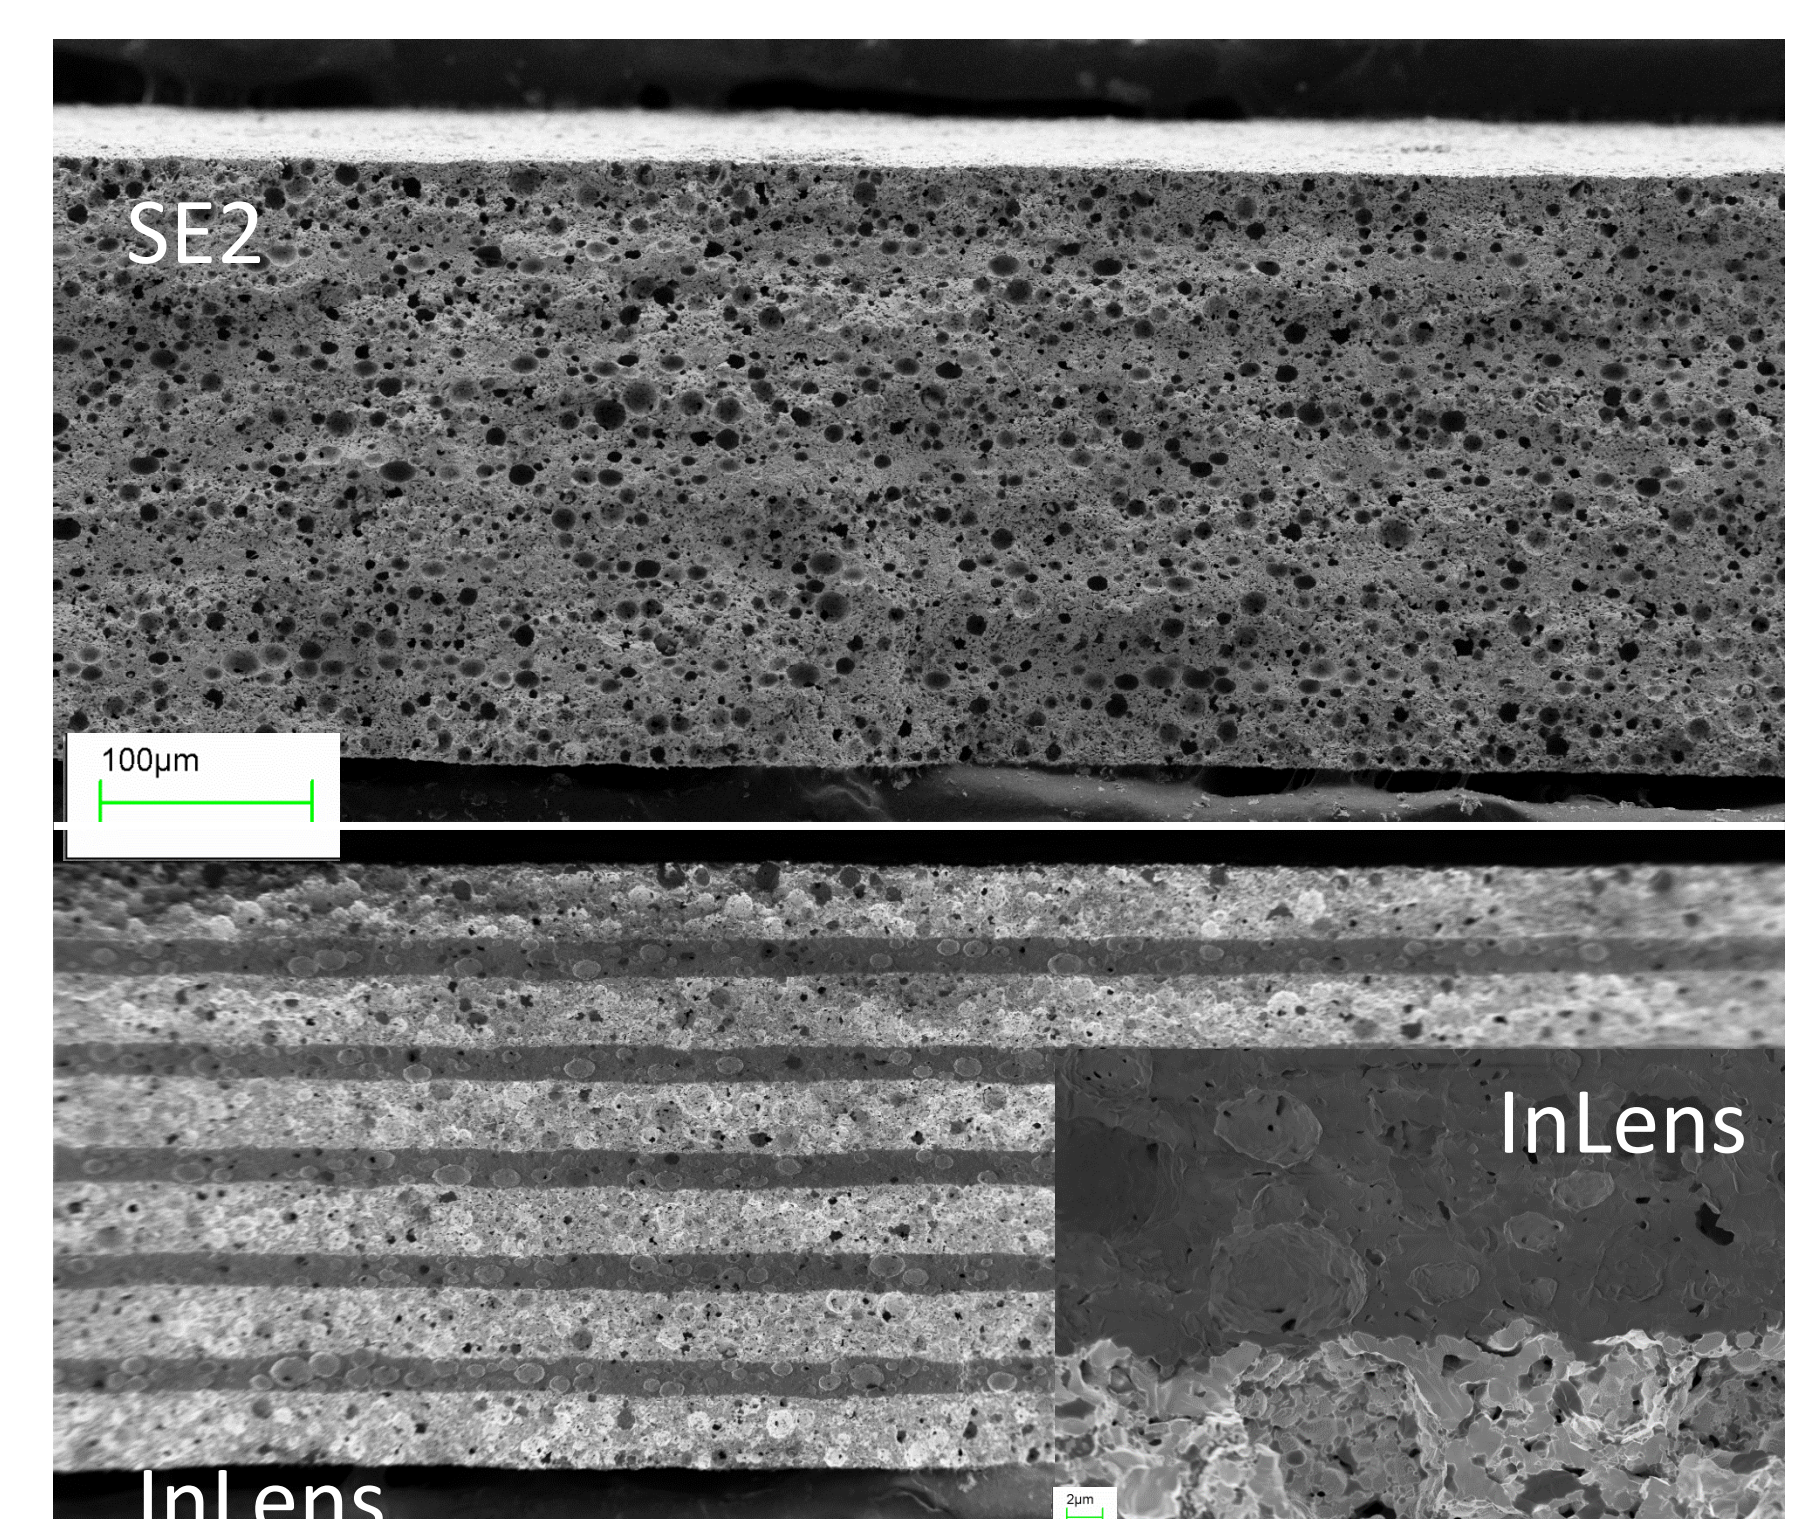

Visualization of electronically percolating phases in electrodes for devices consisting of LSCM/CGO for electrochemical reduction of NO<sub>x</sub> from exhaust gas from vehicles.

## References

1. K. Thydén, Y.L. Liu and J.B. Bilde-Sørensen, *Solid State Ionics* **178**, 1984–1989 (2008)
2. D.C. Joy, Compiled experimental electron scattering data [http://www.mc-set.com/science/eesd/lb\\_load.php](http://www.mc-set.com/science/eesd/lb_load.php)